

Ultrafast optical spin echo for electron spins in semiconductors

Susan M. Clark,¹ Kai-Mei C. Fu,² Qiang Zhang,^{1,3} Thaddeus D. Ladd,^{1,3} Colin Stanley,⁴ and Yoshihisa Yamamoto^{1,3}

¹*Edward L. Ginzton Laboratory, Stanford University, Stanford, California 94305-4088, USA**

²*Quantum Science Research, Hewlett-Packard Laboratories,
1501 Page Mill Road, MS1123, Palo Alto, California 94304*

³*National Institute of Informatics, 2-1-2 Hitotsubashi, Chiyoda-ku, Tokyo 101-8430, Japan*

⁴*Department of Electronics and Electrical Engineering, Oakfield Avenue,
University of Glasgow, Glasgow, G12 8LT, United Kingdom*

Spin-based quantum computing and magnetic resonance techniques rely on the ability to measure the coherence time, T_2 , of a spin system. We report on the experimental implementation of all-optical spin echo to determine the T_2 time of a semiconductor electron-spin system. We use three ultrafast optical pulses to rotate spins an arbitrary angle and measure an echo signal as the time between pulses is lengthened. Unlike previous spin-echo techniques using microwaves, ultrafast optical pulses allow clean T_2 measurements of systems with dephasing times (T_2^*) fast in comparison to the timescale for microwave control. This demonstration provides a step toward ultrafast optical dynamic decoupling of spin-based qubits.

Proposals for spin-based quantum information processors have generated renewed interest in the coherent control and decoherence of electron spins in many environments. Determining the decoherence time, T_2 , for spins has been particularly important in semiconductors since it sets the timescale at which error correction must occur in a semiconductor-spin-based quantum computer [1, 2, 3]. More generally, the measurement of T_2 provides information about noise processes in a spin's environment, which forms the basis for many techniques in magnetic resonance spectroscopy and magnetic resonance imaging.

In some systems, however, measurement of the T_2 decoherence time is obscured by inhomogeneities in spin environments. Spin inhomogeneity causes a perceived loss of coherence, or static dephasing, on a much faster timescale called T_2^* . For an ensemble of spins, this inhomogeneity is due to each spin having a different Larmor frequency due to its local environment [4, 5]. For a single spin, this inhomogeneity is caused by slow environmental changes during temporal averaging [6, 7, 8]. Techniques exist, however, to decouple spins from these inhomogeneous environments [9], but they rely on the coherent manipulation of the spin. If T_2^* is fast compared to the time required to perform this manipulation, these techniques become ineffective. One way around this problem is to use a faster method of spin manipulation. Here, we use ultrafast optical pulses [5, 10, 11, 12, 13, 14] to perform the spin manipulations instead of slower microwave pulses. Ultrafast optical pulses not only allow the efficient refocusing of static dephasing caused by inhomogeneities, but may also provide sufficient speed to enable the dynamic decoupling of spins from the noise sources that cause T_2 decoherence [15, 16, 17, 18, 19].

The simplest method to measure T_2 is the Hahn spin-echo sequence [20], which consists of a $\pi/2$ pulse, a period of free evolution, a π pulse, and then another, equal period of free evolution. This sequence is a workhorse tech-

nique in the fields of nuclear magnetic resonance (NMR) and electron spin resonance (ESR). Recently, this technique has been used to measure T_2 for potential solid-state spin qubits [6, 7, 8, 21, 22]. Another, more indirect way to measure T_2 is via pulsed mode-locking. This technique may be applied in some short- T_2^* systems using trains of ultrafast optical pulses and a T_2 may be extracted by comparing the amount of generated coherence for different pulse train repetition times [23]. This mode-locking technique has recently been modified to observe

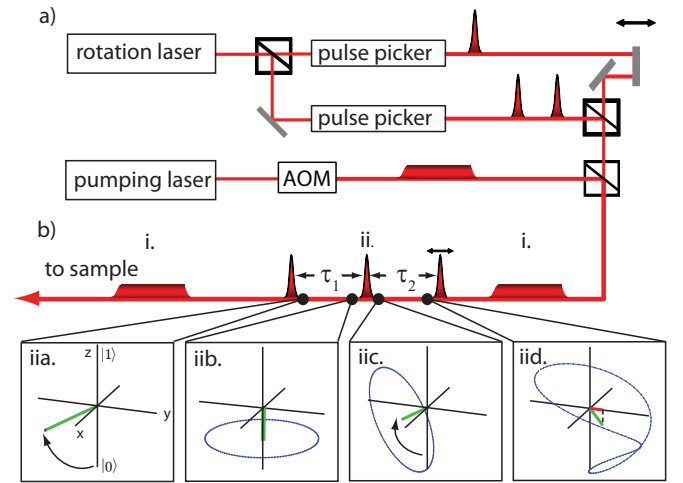


FIG. 1: (Color online) **a)** Experimental setup to generate necessary pulses for all optical spin echo. **b)** Pulse sequence for optical spin echo experiment. The labels i and ii, match those in Fig. 2b. Panels below pulse sequence show the orientation of an ensemble of inhomogeneous spins (blue dots) on the Bloch sphere at different points during a $\pi/3 - \pi/3 - \pi/3$ pulse sequence. The green line shows the average spin polarization vector and the thick red line in panel 2d represents the y -axis projection of the average spin vector. After the final ultrafast pulse and pumping pulse, this projection will be the spin polarization that we observe.

optical spin echo signals [24], however, no measurement of T_2 has yet been made with these echo signals. Additionally, the coherences preserved by modelocking are determined by the polarization of the control pulses, complicating the extension of this technique to the preservation of arbitrary, possibly entangled, spin qubit states.

The Hahn spin-echo technique may be generalized to arbitrary spin-rotation angles. A spin rotation of angle θ due to an ultrafast pulse is modeled as an instantaneous appearance of a large effective field along the x -axis that is much larger than the applied magnetic field in the z -direction. As a result, the rotation is described by an instantaneous unitary rotation operator $R_x(\theta) = \exp(-i\theta S^x)$ for the Pauli spin-operator S^x ($S = 1/2$). Similarly, free rotation about the magnetic field is modeled by a unitary rotation operator about the z -axis, $R_z(\theta)$, where the angle of rotation is determined by $\theta = \omega_n \tau$, where τ is the time of free precession and $\omega_n = g\mu_B B^z(\mathbf{r}_n)/\hbar$ is the Larmor frequency of the n^{th} spin. Here, g is the gyromagnetic ratio for the material, μ_B is the Bohr magneton, and $B^z(\mathbf{r}_n)$ is the magnetic field at each spin position $\mathbf{r}_n$. The Larmor frequency varies from spin to spin primarily due to random nuclear hyperfine fields. Assuming we begin with the n^{th} spin initialized in the spin down state, $|\downarrow\rangle$, the final state of the system, $|\psi_f\rangle_n$, after the sequence of three ultrafast rotations of angles θ_1, θ_2 , and θ_3 , separated by two intervals of free precession for times τ_1 and τ_2 , can be described by

$$|\psi_f\rangle_n = R_x(\theta_3)R_z(\omega_n\tau_2)R_x(\theta_2)R_z(\omega_n\tau_1)R_x(\theta_1)|\downarrow\rangle. \quad (1)$$

In our experiment, we measure probability P that a spin is flipped to the spin up state $|\uparrow\rangle$ averaged over N spins. To model inhomogeneity, we suppose that the Larmor frequencies have a Gaussian probability distribution, so this average projection becomes

$$\begin{aligned} P &= \frac{1}{N} \sum_{n=1}^N |\langle \uparrow | \psi_f \rangle_n|^2 \\ &= \frac{1}{\sqrt{2\pi}\sigma} \int_{-\infty}^{\infty} d\omega |a(\omega)|^2 e^{-(\omega - \omega_0)^2/2\sigma^2}, \end{aligned} \quad (2)$$

where ω_0 is the mean and $\sigma \sim 1/T_2^*$ is the width of the spin resonance distribution. The average projection onto the z -axis is then found to be

$$\begin{aligned} \langle \sigma^z(\tau_1, \tau_2) \rangle &= 2P - 1 = \\ &= -\cos\theta_3 \cos\theta_2 \cos\theta_1 \\ &+ \cos\theta_3 \sin\theta_2 \sin\theta_1 \cos\omega_0\tau_1 e^{-\frac{1}{2}\sigma^2\tau_1^2} \\ &+ \sin\theta_3 \sin\theta_2 \cos\theta_1 \cos\omega_0\tau_2 e^{-\frac{1}{2}\sigma^2\tau_2^2} \\ &+ \sin\theta_3 \cos^2\frac{\theta_2}{2} \sin\theta_1 \cos[\omega_0(\tau_1 + \tau_2)] e^{-\frac{1}{2}\sigma^2(\tau_1 + \tau_2)^2} \\ &- \sin\theta_3 \sin^2\frac{\theta_2}{2} \sin\theta_1 \cos[\omega_0(\tau_1 - \tau_2)] e^{-\frac{1}{2}\sigma^2(\tau_1 - \tau_2)^2}. \end{aligned} \quad (3)$$

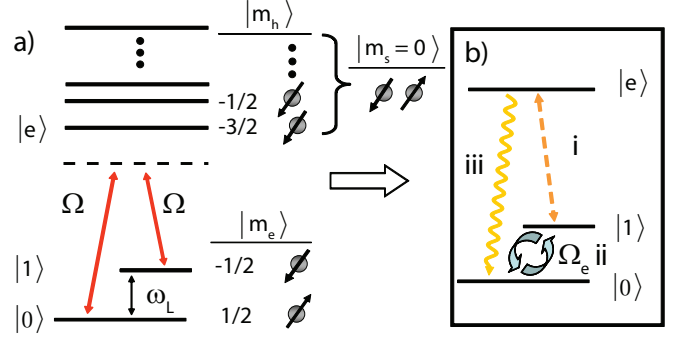


FIG. 2: (Color online) Energy level diagram for a donor bound exciton system in a magnetic field. **a)** Ground states $|0\rangle$ and $|1\rangle$ are split in energy $\hbar\omega_L$ by a magnetic field. They are optically connected to the donor bound exciton states, $|e\rangle$ via a detuned, ultrafast pulse of Rabi frequency Ω . Spins of the relevant levels are shown to the right of the diagram. **b)** Relevant energy levels and applied optical fields in the experiment. The pumping laser applies electric fields on resonance to pump population into the $|0\rangle$ state (orange dashed line, i). The rotation laser performs rotations between the ground states with effective Rabi frequency Ω_e (blue arrows, ii). The pumping laser applies another field on resonance (i) and light is collected from the $|0\rangle \leftrightarrow |e\rangle$ transition (yellow line, iii)

Most of the terms in Eq. 3 result in polarizations that rapidly vanish due to T_2^* dephasing as the time between pulses is increased, but the last term describes a spin-echo which is immune to static T_2^* dephasing. This term is maximized for the Hahn echo condition $\theta_1 = \theta_3 = \pi/2$ and $\theta_2 = \pi$. The Hahn echo condition, however, is not required to see the echo; there will still be a finite polarization for almost any angle of the three pulses. For one visualization of how the spins refocus in the small angle case, refer to the panels in Fig. 1. This generalization is particularly important when using ultrafast pulses, because the decoherence induced by the pulses themselves may increase with angle [12].

We applied this sequence of three optical rotations to an ensemble of electron spins bound to neutral Si donors in GaAs [25]. For this material, high pulse powers induce additional decoherence, limiting θ to values less than about $\pi/3$ [12]. An energy level diagram of this system in an applied magnetic field is shown in Fig. 2a. The ground states are formed by a single electron spin bound to a Si donor in GaAs. They are denoted $|0\rangle$ and $|1\rangle$ depending on the spin of the electron and are split by an energy $\hbar\omega_L \approx 50$ GHz via a magnetic field, $B_{\text{ext}} = 10$ T. These ground states are optically connected to the donor-bound-exciton (D^0X) state (denoted $|e\rangle$), which consists of an additional electron-hole pair. Despite the many excited states of the donor-bound-exciton system, we can approximate the ground states as a two-level system via adiabatic elimination of the excited states (valid if the detuning, $\Delta = 1$ THz, is much larger than other rates in the

system). The ultrafast pulse (2 ps) couples states $|0\rangle$ and $|1\rangle$ with an effective Rabi frequency, $\Omega_e \sim \Omega^2/\Delta$, where Ω is the instantaneous optical Rabi frequency [3, 12, 14]. For our experiments, the pulse width of the ultrafast pulse is held constant, so the power of the pulse determines the spin rotation angle.

The experimental setup to generate this pulse sequence is shown in Fig. 1a and the pulse sequence used to perform the spin echo measurement is depicted in Fig. 1b. First we initialize the spins to the $|0\rangle$ state by applying a long pulse from a continuous-wave ring laser (labeled “pumping laser” in Fig. 2a) gated by an acousto-optic modulator (AOM) resonant on the $|1\rangle \leftrightarrow |e\rangle$ transition (labeled i in Fig. 1b and Fig. 2b). The first and second rotation pulses are picked from a pulse train of a Ti:Sapphire modelocked laser (“rotation laser”) by a pulse picker (electro-optic modulator (EOM) followed by an AOM for improved extinction ratio) and are separated by τ_1 , which is always a multiple of the repetition time of the laser (13.2 ns). The third pulse arrives at a time τ_2 after the second pulse, which is determined by both a pulse picker and an optical delay line which can vary τ_2 by 10s of picoseconds. In order to measure rephasing, the difference between the free evolution times, $|\tau_2 - \tau_1|$, is kept smaller than the 1 ns T_2^* dephasing time [4]. We determine the final state of the system by projecting the rephased spin polarization vector onto the z -axis with the application of another long pulse (μs) from the pumping laser on resonance with the $|1\rangle \leftrightarrow |e\rangle$ transition (labeled i in Fig. 1b and Fig. 2b). We monitor the spontaneous emission at the frequency of the $|0\rangle \leftrightarrow |e\rangle$ transition (labeled iii in Fig. 2b), which will be proportional to the amount of population in state $|1\rangle$. We filter out pump laser scatter from the spontaneous emission signal via a monochromator and polarization selection rules. The final signal is measured with an avalanche photodiode.

For these ultrafast rotations, only the arrival time of the pulse determines the phase of the rotation [3], so the optical phase of the pulse does not need to be externally stabilized. However, the pulse arrival time needs to be stabilized to much less than the Larmor frequency of the spin system. The jitter of the modelocked Ti:Sapphire laser was measured using a technique described by von der Linde [26] and was found to be about 1 ps over a millisecond timescale. By keeping τ_1 and τ_2 less than a millisecond, individual pulses picked from the modelocked train can be used for this pulse sequence without external stabilization.

The results of the experiment can be seen in Fig. 3. When we apply only two pulses, as in a Ramsey fringe experiment, we see no fringes (Fig. 3a, solid green line) for pulse separations greater than 26 ns, indicating that the spins are completely dephased. When we add a third pulse, we recover fringes that have a frequency equal to the Larmor frequency (blue dots and red dashed line in Fig. 3a and b) which is evidence of the echo.

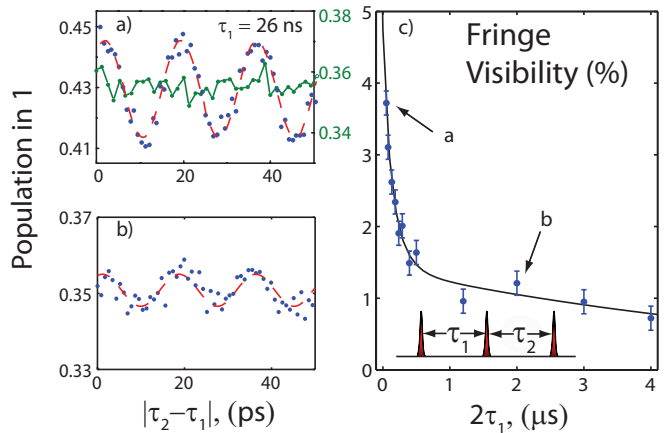


FIG. 3: (Color online) Results of all-optical spin echo experiment **a)** Population in $|1\rangle$ as second pulse is scanned in a two pulse experiment where $\tau_1 = 26$ ns (solid green line). No fringes can be seen, indicating complete dephasing. The blue dots and dotted red curve are data and a fit respectively to a three pulse experiment with $\tau_1 = 26$ ns. For the three pulse experiment, there are clear oscillations. **b)** Population in $|1\rangle$ as τ_2 is scanned for $2\tau_1 = 2$ μs (blue dots) and the fit to a sine function (red dashed line). The visibility is 1.2 %. **c)** Fringe visibility vs. pulse separation between first and last pulse, $2\tau_1$. Error bars are calculated from the standard deviation of several measurements of the fringe visibility at one point. The fit is a phenomenological decay (black solid line) that includes a pulse induced decoherence and an intrinsic T_2 decoherence with a decay time of 6.7 ± 2.5 μs . The points shown in a) and b) are labeled.

Some fluctuations in the experiment cause a small linear drift of random direction and amplitude in the overall detector count-rate. We remove the drift by fitting each fringe curve to a sum of terms constant, linear, and oscillatory in τ_2 , and then subtracting the linear term. We calculate the visibility for each fringe curve as $V = (\max - \min)/(\max + \min)$, where max and min are the maximum and minimum of the fitted sine curve. In Fig. 3c we see the decay of the fringe visibility with pulse separation, indicating decoherence in this system.

The data in Fig. 3c are well described by a phenomenological model with two sources of decoherence. The first source is intrinsic to the sample and leads to a decay of the echo with rate T_2^{-1} . The second source is generated by the pulses themselves. It is known that the rotation pulses have a finite fidelity due to a decoherence source generated by the pulses. It was found in Ref. [12] that as more pulse power is applied, there appears a new dephasing of the bound-exciton state that is proportional to pump power. This dephasing may be due to local heating resulting from background absorption of the laser, which induces some population of phonons or other excitations, such as excited impurity states. In our model, these pulse-induced remnant excitations also decohere the spins at a rate proportional

to their population. Since the spurious excitation is assumed to equilibrate at some timescale T_h , we presume this effect vanishes in time as $\exp(-t/T_h)$, and so a coherence $\langle\sigma^+\rangle$ obeys a Bloch equation of the form

$$\frac{d}{dt}\langle\sigma^+(t)\rangle_n = \left[i\omega_n - \frac{1}{T_2} - Re^{-t/T_h}\right]\langle\sigma^+(t)\rangle_n, \quad (4)$$

which may be analytically integrated.

Using this decoherence model, the visibility for $\tau_1 = \tau_2 = \tau \gg T_2^* \sim 1/\sigma$ is

$$V(\tau) = V_0 e^{-2\tau/T_2 - 2RT_h[1 - \exp(-\tau/T_h)]}. \quad (5)$$

This curve is fit to the visibility data in Fig. 3c (black line). The resulting fitting parameters are the intrinsic decoherence time $T_2 = 6.7 \pm 2.5 \mu\text{s}$; the pulse-induced decoherence time $R^{-1} = 175 \pm 30 \text{ ns}$; the relaxation rate of the excitations contributing to pulse-induced decoherence $T_h = 100 \pm 20 \text{ ns}$; and the initial visibility before decay $V_0 = 0.047 \pm 0.003$. This last parameter V_0 may be estimated from Eq. (3) as

$$V_0 = \langle\sigma^z\rangle_0 \frac{D(\theta_1)D(\theta_2)\sin(\theta_3)\sin(\theta_2^2/2)\sin(\theta_1)}{1 - \langle\sigma^z\rangle_0 \cos(\theta_3)\cos(\theta_2)\cos(\theta_1)}, \quad (6)$$

where $\langle\sigma^z\rangle_0$ is the initial polarization created by optical pumping and $D(\theta)$ is the amount of spin decoherence created by a single pulse of angle θ . Both of these may be estimated from previous studies [12] as $D(\theta) \approx 1 - 0.25\theta$ and $\langle\sigma^z\rangle \approx 0.9$, leading to a V_0 of 5 %, in agreement with the fit.

The measured $T_2 = 6.7 \pm 2.5 \mu\text{s}$ is consistent with previous measures of T_2 in quantum dot systems using microwave spin echo [6, 7] and mode-locking [23]. A microsecond T_2 , however, is still orders of magnitude shorter than the theoretical maximum of twice the spin relaxation time ($2T_1$) [27], which has been measured to be milliseconds in this sample [28]. This observation indicates that there are sources of dynamic decoherence, most likely nuclear spin diffusion, which has been theoretically predicted to cause coherence decay on this timescale [29, 30, 31]. This type and other types of dynamic decoherence, however, can be reversed using a series of π -pulses applied faster than the characteristic timescale of decoherence [15, 16, 17, 18, 19], therefore extending the T_2 time of the system. In cases where π -pulses are not possible, a series of small-angle pulses can be applied over several Larmor periods to sum to a π -pulse [12]. Because optical pulses can be applied more quickly than microwave pulses, the demonstration in this paper is a critical step towards eliminating decoherence that occurs on a fast timescale, potentially making many more materials suitable for applications requiring long T_2 .

In conclusion, we have demonstrated that three ultra-fast optical pulses can produce an echo signal to measure

the T_2 time of electron-spin systems. Although here we applied this technique to Si:GaAs, we believe it has potential applications in other materials relevant to magnetic resonance, particularly those with fast decoherence times. We have also demonstrated that partial rephasing is possible even when π and $\pi/2$ pulses are unavailable, meaning the technique can be applied when a system has a small optical dipole moment, when only low laser power is available, or when optical dephasing is present. Lastly, optical pulses have the potential to extend the decoherence time in semiconductor systems by dynamical decoupling, allowing more materials to be suitable for application that require long T_2 times. Such a scheme could be used to extend the spin-memory time of a spin-based quantum computer and can be integrated into quantum bus schemes for quantum computing [3].

S. M. C. was partially supported by the HP Fellowship Program through the Center for Integrated Systems. This work was financially supported by the MURI Center for photonic quantum information systems (ARO/ARDA Program DAAD 19-03-1-0199), JST/SORST program for the research of quantum information systems for which light is used, University of Tokyo Special Coordination Funds for Promoting Science and Technology, and MEXT, NICT.

* Electronic address: sclark4@stanford.edu

- [1] D. Loss and D. P. DiVincenzo, Phys. Rev. A **57**, 120 (1998).
- [2] A. Imamoglu et al., Phys. Rev. Lett. **83**, 4204 (1999).
- [3] S. M. Clark, K.-M. C. Fu, T. D. Ladd, and Y. Yamamoto, Phys. Rev. Lett. **99**, 040501 (2007).
- [4] K.-M. C. Fu et al., Phys. Rev. Lett. **95**, 187405 (2005).
- [5] M. V. G. Dutt et al., Phys. Rev. B **74**, 125306 (2006).
- [6] J. R. Petta et al., Science **309**, 2180 (2005).
- [7] F. H. L. Koppens, K. C. Nowack, and L. M. K. Vandersypen, Phys. Rev. Lett. **100**, 236802 (2008).
- [8] R. Hanson, V. V. Dobrovitski, A. E. Feiguin, O. Gywat, and D. D. Awschalom, Science **320**, 352 (2008).
- [9] C. P. Slichter, *Principles of Magnetic Resonance* (Springer, New York, 1996).
- [10] J. A. Gupta, R. Knobel, N. Samarth, and D. D. Awschalom, Science **292**, 2458 (2001).
- [11] S. E. Economou, L. J. Sham, Y. Wu, and D. G. Steel, Phys. Rev. B **74**, 205415 (2006).
- [12] K.-M. C. Fu, S. M. Clark, C. Santori, C. Stanley, M. C. Holland, and Y. Yamamoto, Nat. Phys. **4**, 780 (2008).
- [13] J. Berezovsky, M. H. Mikkelsen, N. G. Stoltz, L. A. Coldren, and D. D. Awschalom, Science **320**, 349 (2008).
- [14] D. Press, T. D. Ladd, B. Zhang, and Y. Yamamoto, Nature **456**, 218 (2008).
- [15] L. Viola and S. Lloyd, Phys. Rev. A **58**, 2733 (1998).
- [16] W. M. Witzel and S. D. Sarma, Phys. Rev. Lett. **98**, 077601 (2007).
- [17] W. Yao, R.-B. Liu, and L. J. Sham, Phys. Rev. Lett. **98**, 077602 (2007).
- [18] G. S. Uhrig, Phys. Rev. Lett. **98**, 100504 (2007).

- [19] B. Lee, W. M. Witzel, and S. Das Sarma, Phys. Rev. Lett. **100**, 160505 (2008).
- [20] E. L. Hahn, Phys. Rev. **80**, 580 (1950).
- [21] F. Jelezko, T. Gaebel, I. Popa, A. Gruber, and J. Wrachtrup, Phys. Rev. Lett. **92**, 076401 (2004).
- [22] R. Hanson, O. Gywat, and D. D. Awschalom, Phys. Rev. B **74**, 161203 (2006).
- [23] A. Greilich et al., Science **313**, 341 (2006).
- [24] A. Greilich et al., Nat. Phys. (2009), advance online publication DOI:10.1038/NPHYS1226.
- [25] V. A. Karasyuk et al., Phys. Rev. B **49**, 16381 (1994).
- [26] D. von der Linde, Appl. Phys. B **39**, 201 (1986).
- [27] W. A. Coish and D. Loss, Phys. Rev. B **70**, 195340 (2004).
- [28] K.-M. C. Fu, W. Yeo, S. Clark, C. Santori, C. Stanley, M. C. Holland, and Y. Yamamoto, Phys. Rev. B **74**, 121304(R) (2006).
- [29] D. Paget, Phys. Rev. B **25**, 4444 (1982).
- [30] R. de Sousa and S. Das Sarma, Phys. Rev. B **67**, 033301 (2003).
- [31] W. Yao, R.-B. Liu, and L. J. Sham, Phys. Rev. B **74**, 195301 (2006).